

Multiple Andreev reflections spectroscopy of two-gap 1111- and 11 Fe-based superconductors

Ya.G. Ponomarev · S.A. Kuzmichev · T.E. Kuzmicheva ·
M.G. Mikheev · M.V. Sudakova · S.N. Tchesnokov · O.S. Volkova ·
A.N. Vasiliev · Yu.F. Eltsev · V.M. Pudalov · A.V. Sadakov ·
A.S. Usol'tsev · Th. Wolf · E.P. Khlybov

Received: date / Accepted: date

Abstract The “break-junction” technique was used to prepare superconductor - constriction - superconductor (ScS) nanocontacts in polycrystalline samples of Fe-based superconductors $\text{CeO}_{0.88}\text{F}_{0.12}\text{FeAs}$ (Ce-1111; $T_C^{\text{bulk}} = 41 \pm 1$ K), $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$ (La-1111; $T_C^{\text{bulk}} = 28 \pm 1$ K), and FeSe ($T_C^{\text{bulk}} = 11 \pm 1$ K). Two sets of subharmonic gap structures were detected due to multiple Andreev reflections effect, indicating the presence of two nodeless superconducting gaps with the BCS-ratios $2\Delta_L/k_B T_C = 4.2 \div 5.9$ and $2\Delta_S/k_B T_C \ll 3.52$, respectively. Temperature dependences $\Delta_{L,S}(T)$ in FeSe indicate a k -space proximity effect between two superconducting condensates. A linear relation between the gap Δ_L and magnetic resonance energy $E_{\text{res}} \approx 2\Delta_L$ is found to be valid for iron-based superconductors.

Keywords Fe-based superconductors · two-gap superconductivity · multiple Andreev reflections · subharmonic gap structure · “break-junction”

PACS 74.70.Xa · 74.25.-q · 74.45.+c

Ya.G. Ponomarev · S.A. Kuzmichev · M.G. Mikheev ·
M.V. Sudakova · S.N. Tchesnokov · O.S. Volkova ·
A.N. Vasiliev

Lomonosov Moscow State University, 119991 Moscow, Russia
T.E. Kuzmicheva
Lebedev Physical Institute RAS, 119991 Moscow, Russia
Lomonosov Moscow State University, 119991 Moscow, Russia

Yu.F. Eltsev · V.M. Pudalov · A.V. Sadakov · A.S. Usol'tsev
Lebedev Physical Institute RAS, 119991 Moscow, Russia

Th. Wolf
Karlsruher Institut für Technologie, Institut für
Festkörperphysik, D-76021 Karlsruhe, Germany

E.P. Khlybov
Institute for High Pressure Physics RAS, 142190 Troitsk,
Russia

1 Introduction

Andreev spectroscopy [1] is a powerful instrument to measure superconducting gap in a wide temperature range up to T_C [2,3,4]. A number of such measurements have been performed on oxypnictides $\text{RFeAsO}_{1-x}\text{F}_x$ and FeSe [5,6,7,8]. Here we present a systematic study of current-voltage characteristics (CVCs) and dynamic conductance $dI(V)/dV$ for ScS-contacts in Ce-1111, La-1111 and FeSe by intrinsic multiple Andreev reflections effect (IMARE) spectroscopy, the superconducting gap values determination, as well as the gap temperature dependences in FeSe . The compounds under study belong to the class of iron-based superconductors discovered in 2008 [9]. They are characterized by a layered crystal structure and a presence of electron and hole quasi-two-dimensional Fermi surface sheets where two superconducting condensates are supposed to be formed at $T < T_C$ [5].

2 Experimental details

To measure the superconducting gaps, the two methods were used: (1) Andreev spectroscopy [1] of single ScS nanocontacts [2] and (2) “intrinsic” Andreev spectroscopy of ScS-contact stacks. The nanocontacts into polycrystalline samples were formed by a “break-junction” technique [10].

To interpret the measured dynamic conductance spectra of the symmetric ScS-contacts we used theoretical model by Kümmel *et al.* [2]. The main features of the $I(V)$ curves for our ScS-contacts comprise a pronounced excess current at low bias voltages and a sub-

harmonic gap structure (SGS) in the dI/dV curve. The latter shows sharp dips at bias voltages [2]:

$$V_n = \frac{2\Delta}{en}, \quad n = 1, 2 \dots \quad (1)$$

With the number n raising up, the minima amplitude decays exponentially. In the case of a two-band superconductor, two distinct SGS of such a kind should be observed. Using a linear $V_n(1/n)$ dependence which passes through $(0;0)$ point, it is easy to determine the gap value accurately.

Studies of the SGS in CVC of individual Sharvin type [11] ScS-nanocontacts allow to gain information even in the case of inhomogeneous samples. To make the SGS observable, the size a of an Andreev contact should be chosen significantly smaller than the mean free path l of quasiparticles (the ballistic regime) [2,3,4].

Due to the layered structure of Fe-based superconductors, the nanosteps in the c -direction actually represent stacks of a limited number of ballistic SnS-junctions causing an intrinsic multiple Andreev reflections effect, which is similar to the intrinsic Josephson effect in SIS-array [12]). Using stacks of contacts, one can exclude surface distortion of superconductivity and observe sharp peculiarities guaranteed corresponding to the *bulk gaps*. Bias voltages of these singularities scale with the number of contacts N in a stack.

For temperatures up to T_C , the gap Δ may be obtained directly by substituting to Eq.(1) the bias voltages corresponding to the dips [2]. The data obtained (Figs. 2-7) are typical for clean classical SnS-contacts [2] and indeed, as it will be pointed out below, show two distinct sequences of dips.

The CVC and their derivatives $dI(V)/dV$ were obtained by a computer controlled set-up using a NI digital board. The dynamic conductance spectra were measured with a standard modulation technique [13].

3 Experimental results

3.1 $\text{CeO}_{1-x}\text{F}_x\text{FeAs}$

In this section, Andreev spectroscopy data for Ce-1111 break junctions at $T = 4.2\text{ K}$ are presented, evaluating two superconducting gaps *for the first time*. The synthesis of polycrystalline $\text{CeO}_{0.88}\text{F}_{0.12}\text{FeAs}$ samples with $T_C^{\text{bulk}} \approx 41\text{ K}$ (see Fig.1) is described in [14].

Dynamic conductance for three single ScS-contacts #d1, #d2 (sample Ce1 (marked as 1 and 2)), and #d6 (sample Ce2 (3)) is shown at Fig.2. Two sets of SGS were detected. The large gap minima marked by shaded

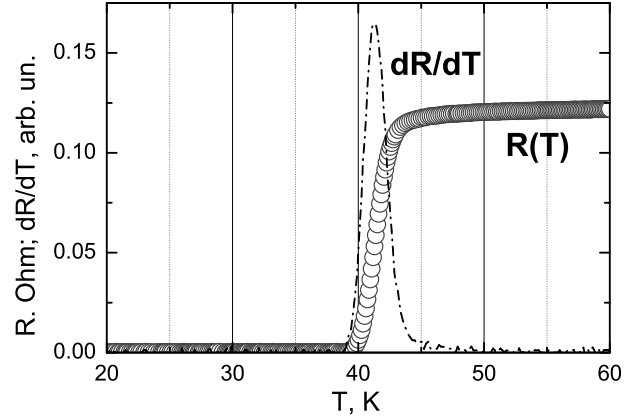


Fig. 1 Resistive transition for $\text{CeO}_{0.88}\text{F}_{0.12}\text{FeAs}$ sample ($T_C^{\text{bulk}} = 41 \pm 1\text{ K}$).

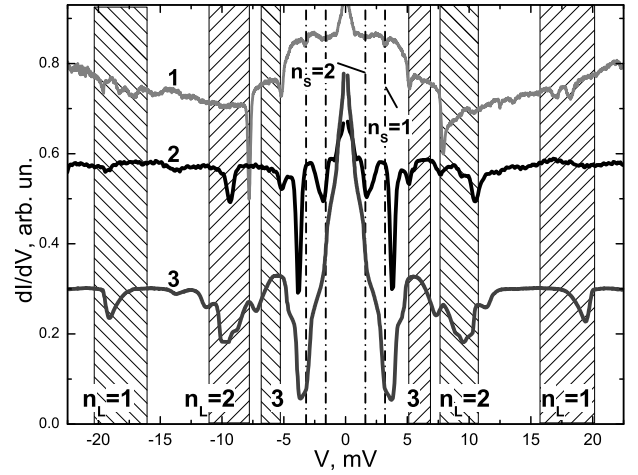


Fig. 2 dI/dV -characteristics of Ce-1111 nanocontacts: sample Ce1, contacts #d1 (1) and #d2 (2), and sample Ce2, contact #d6 (3) ($T = 4.2\text{ K}$). Two sets of SGS corresponding to gaps $\Delta_L \approx 9\text{ meV}$ (marked by n_L labels and dashed areas covering a 10% uncertainty for the large gap value) and $\Delta_S \approx 1.6\text{ meV}$ (dash-dotted vertical lines n_S labels) are detected. The curves are shifted along the vertical scale for the sake of clarity

areas (covering a 10% uncertainty) and n_L labels, in accordance with eq. (1), lead to the value $\Delta_L = (9.0 \pm 1.0)\text{ meV}$. The $n_L = 1$ minima reduced intensity may be caused by a slight overheating of the contact area. Since Andreev spectroscopy is insensitive to the direction in k -space, spectra obtained by us show dispersion due to gap anisotropy. The latter could be an origin of a fine structure within the large gap SGS. The small gap SGS starts with minima located at $V_{S1} \approx 3.3\text{ mV}$ (marked by dash-dotted vertical lines and n_S labels), which exhibit a rather high relative amplitude than the third Andreev dips' for the large gap one; the $n_S = 2$ dips are located at $V_{S2} \approx 1.6\text{ mV}$. Therefore, the SGS define the small gap value $\Delta_S = (1.6 \pm 0.2)\text{ meV}$. Linear dependence of

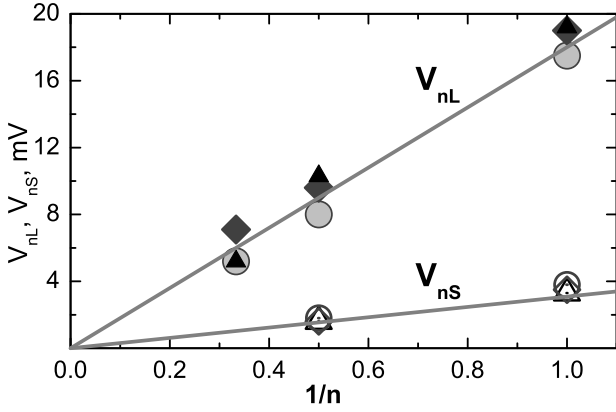


Fig. 3 The dependences of bias voltages $V_{nL} = 2\Delta_L/en_L$ and $V_{nS} = 2\Delta_S/en_S$ on $1/n$ for the investigated Andreev ScS nanocontacts (see Fig. 2): sample Ce1, contacts #d1 (circles) and #d2 (triangles), and sample Ce2, contact #d6 (rhombs). Averaged gap values are $\Delta_L = 9 \pm 1$ meV, $\Delta_S = 1.6 \pm 0.2$ meV

Andreev minima positions for the large and the small gap $V_{nL,S}$ versus their reversed number, $1/n$, plotted in Fig. 3, demonstrates unambiguously that the dips observed in Fig. 2 do form two independent SGS indicating the presence of two nodeless superconducting gaps. Taking into consideration the bulk T_C of the samples, the BCS ratio for the large gap is $2\Delta_L/k_B T_C^{bulk} \approx 5.1$; for the small gap $2\Delta_S/k_B T_C^{bulk} \approx 0.9$.

3.2 $\text{LaO}_{1-x}\text{F}_x\text{FeAs}$

Polycrystalline $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$ (LOFA) samples with bulk $T_C^{bulk} = (28 \pm 1)$ K were used, where about 50 ScS-Andreev $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$ contacts were studied. The dynamic conductance $dI(V)/dV$ of single contacts and nanosteps demonstrates two well-reproducible sets of SGS corresponding to the pair of independent gap values. The number N of elementary contacts in the nanosteps was controlled by comparison of a single contact $dI(V)/dV$ spectra with dynamic conductance characteristics of several stacks normalized to a single junction spectrum. Figure 4 shows $dI(V)/dV$ spectra for a single contact #d17 (thin dotted curve) and for the stacks #d9 and #d10 with different number of junctions in the array ($N = 2$, bold black curve and $N = 4$, dash-dotted curve respectively). Scaling of the SGS with properly selected number of contacts N in nanosteps is straightforward. Following the equation of Kümmel *et al.* [2], we easily obtain the large gap $\Delta_L \approx 6.1$ meV. As for the small gap minima, $2\Delta_S$ peculiarities marked by arrows (at the top of Fig. 4 and in the inset) give $\Delta_S = 0.8$ meV and 1.25 meV values at $T = 4.2$ K for the single contact #d17 and for the array #d9, respec-

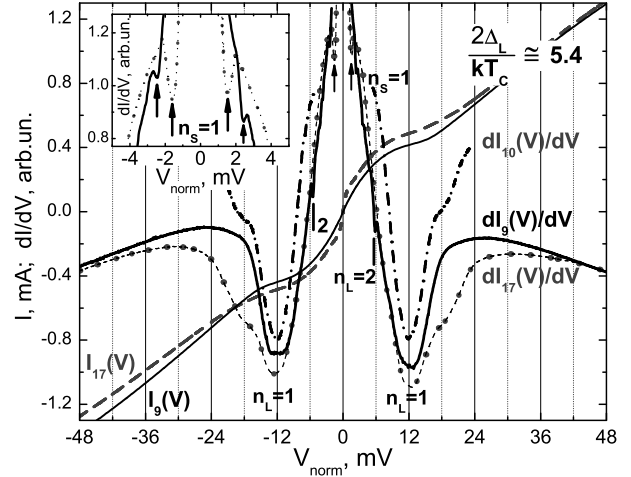


Fig. 4 Normalized CVC and dynamic conductance of ScS-Andreev contacts in $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$ sample LOFA5: contacts #d10 ($N = 4$ junctions in a stack), #d9 ($N = 2$), both normalized to #d17 (single ScS-junction, marked by dots). $T_C^{local} \approx 26$ K. The SGS for the large gap (n_L labels) gives $\Delta_L \approx 6.1$ K for all the contacts, the small gap $\Delta_S \approx 0.8$ K (contact #d17) and 1.25 meV (contact #d9) SGSs are marked by black arrows and n_S labels. **Inset** shows details of small gap SGS for contacts #d17 and #d9 (from Fig. 4)

tively. The critical temperature in the contact region T_C^{local} was found with a help of $\Delta_{L,S}(T)$ dependence. The values obtained $\Delta_L \approx 6.1$ meV, $\Delta_S \approx 1.25$ meV, and $T_C^{local} = 26 \pm 1$ K are close to the results of [15].

Figure 5 shows normalized CVC and dynamic conductance of two-contact ScS-Andreev array #d14 in another $\text{LaO}(\text{F})\text{FeAs}$ sample. Sharp SGS related to the large gap (marked by black n_L labels) gives $\Delta_L \approx 4.5$ meV (see solid squares in the inset to Fig. 2). All these Andreev minima up to $n = 5$ are double-split. It seems that the doublets observed on the high-quality characteristics are caused by some anisotropy of the Δ_L order parameter, though it has no nodes, as was shown in [6]. The CVC at Fig. 5 demonstrates a small Josephson supercurrent at zero bias caused by the tunneling between the sample clefts. An SGS associated with the small gap (gray n_S labels and black arrows) leads to $\Delta_S \approx 0.8$ meV (see open squares at the inset to Fig. 5).

The BCS-ratio $2\Delta_L/k_B T_C^{local} = (4.2 \div 5.6)$ (T_C^{local} is the T_C of the contact area) exceeds 3.52-value and thus is in favor of a strong coupling in Δ_L condensate. At the same time, $2\Delta_S/k_B T_C^{local} < 1.2$ is a result of induced superconductivity at finite temperatures in the bands with the small gap. These values support data reported earlier in [6] and are in close agreement with the experimental results on $\text{GdO}(\text{F})\text{FeAs}$ [7] and our data on MgB_2 published in [16, 18].

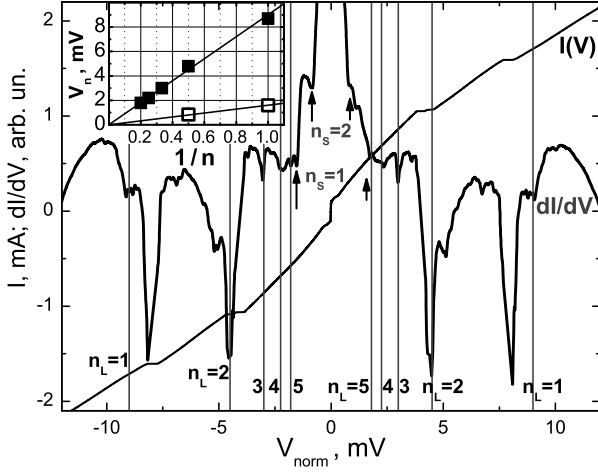


Fig. 5 Normalized CVC and dynamic conductance of ScS-Andreev two contacts array #d14 (sample LOFA4). The SGS related to the large gap (n_L labels) gives $\Delta_L \approx 4.5$ meV (the region with a slightly reduced superconductivity). Thin vertical lines represent the expected location of Andreev minima in accordance with theoretical formula $V_n = 2\Delta/en$ from [2]. The small gap peculiarities (light n_S labels and black arrows) lead to $\Delta_S \approx 0.8$ K. (**Inset**) The $V_n(1/n)$ dependences plotted for the SGS minima of both gaps (from Fig. 5). Lines average the experimental values

3.3 FeSe

Among the new class of Fe-based superconductors [9], layered FeSe has the simplest crystal structure and relatively low critical temperature T_C . Polycrystalline FeSe samples have been grown from melt by spontaneous nucleation. The synthesis process was described in detail in [8]. The intrinsic multiple Andreev reflections effect (IMARE) was observed in FeSe nanosteps earlier [8].

Figure 6 represents $I(V)$ and $dI(V)/dV$ characteristics for several ScS-junctions in FeSe formed by successive mechanical readjustments of the contact. Two sets of SGS with a limited number of dips are detected. The first set of dips (marked by n_L labels) gives the large gap value $\Delta_L \approx 2.6$ meV. The second set of dips (n_S labels) corresponds to the small gap $\Delta_S \approx 1$ meV. It is worth to note that the dip positions and, consequently, the gap values remain unchanged in the process of readjustment of the contact. This proves the high homogeneity of the sample superconducting properties in the contact area. Summarizing the data for more than 30 ScS-contacts, the averaged superconducting gap values are $\Delta_L = 2.8 \pm 0.4$ meV and $\Delta_S = 0.8 \pm 0.2$ meV ($T = 4.2$ K, $T_C^{bulk} = 12 \pm 1$ K) [8].

Figure 7 shows the temperature dependences of the gaps $\Delta_{L,S}(T)$ for two ScS-contacts in FeSe. The $\Delta_L(T)$ -curve lies slightly below the standard BCS-like dependence. The $\Delta_S(T)$ dependence for the small gap devi-

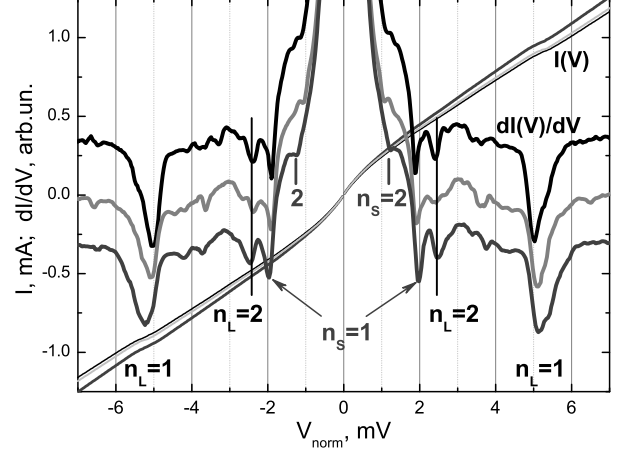


Fig. 6 Normalized to a single junction $I(V)$ and $dI(V)/dV$ characteristics for ScS-Andreev contacts in FeSe (sample FS1, contacts #d8, #d9, #d11 of three SnS-junctions in a stack; $T_C = 12.5$ K, $T = 4.2$ K). Two SGS at bias voltages $V_{nL,S} = 2\Delta/en_{L,S}$ corresponding to the large (n_L labels) and the small gap (n_S labels) yield the values $\Delta_L \approx 2.6$ meV and $\Delta_S \approx 1$ meV

ates from the BCS-type curve and is in a good agreement with the calculations in [17]. Knowing the local $T_C^{local} \approx 9.7$ K, one can calculate the BCS-ratio. For the large gap, we obtain $2\Delta_L/k_B T_C^{local} \approx 5.7$ which exceeds the BCS value 3.52 for a single-gap superconductor. On the other hand, for the small gap Δ_S the ratio $2\Delta_S/k_B T_C$ is much smaller than 3.52. Such a behavior resembles the situation in MgB_2 [18, 19, 20] and, by parity of reasoning, can be explained by k -space proximity effect [21, 22] between two superconducting condensates, where the large gap condensate plays a “driving” role.

4 Discussion

It was pointed out [23] that inelastic neutron scattering data can provide a valuable information about the symmetry of the superconducting gap in novel superconductors. Calculations showed, in particular, that a hump structure must appear in the dynamic spin susceptibility just above the 2Δ energy in the case of an s^{++} wave state (the fully gapped s -wave state without sign reversal) [23]. Recently, the experimental linear dependence of the spin resonance energy E_{res} on T_C with the average slope $4.7k_B T_C$ was presented for several iron based superconductors (Fig. 5 in [24]). Within experimental errors, this dependence is coincident with the plot of the superconducting gap parameter $2\Delta_L$ vs the T_C for iron based superconductors: Ce-1111 (present investigation), FeSe ([8]), LaO(F)FeAs [6], GdO(F)FeAs [7], as well as KFe_2As_2 , $FeTe_{1-x}Se_x$, $LiFeAs$, (see Fig.

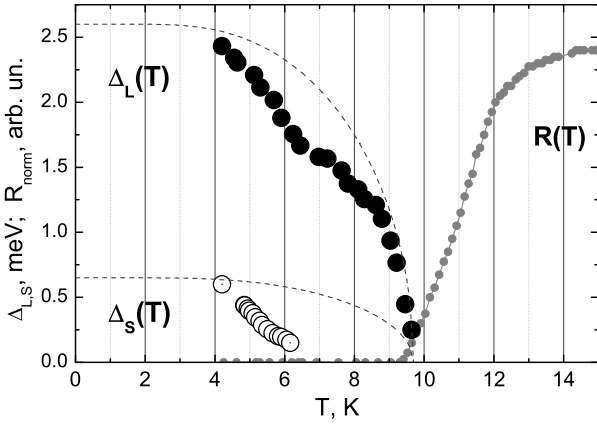


Fig. 7 Temperature dependence of two superconducting gaps $\Delta_L(T)$ (sample FS1, contact $b\ddagger$; $\Delta_L(T = 4.2 \text{ K}) = 2.4 \pm 0.2 \text{ meV}$) and $\Delta_S(T)$ (sample FS2, contact $\ddagger b$; $\Delta_S(4.2 \text{ K}) = 0.7 \pm 0.1 \text{ meV}$). Local $T_C^{\text{local}} = 9.7 \pm 0.5 \text{ K}$. Single-gap BCS-like curves (dashed lines), and the normalized sample resistance $R_{\text{norm}}(T)$ (gray circles) are presented for comparison

11 in [8] and Refs. therein). Although the scattering of data is quite significant (Fig. 8), two linear dependences emerge with $2\Delta_L/k_B T_C = 4.8 \pm 1.0$ and $2\Delta_S/k_B T_C = 1.1 \pm 0.4$. The coincidence of $2\Delta_L/k_B T_C$ (Fig. 8) and $E_{\text{res}}/k_B T_C$ (Fig. 5 in [24]) supports the version of a fully gapped s -wave state without sign reversal [23].

In conclusion, properties of CeO(F)FeAs, LaO(F)FeAs, and FeSe superconductors were studied by ScS-Andreev and IMARE spectroscopies. The dynamic conductance curves of single and stack ScS-contacts cannot be described within the single-gap framework and evidence for the two-gap superconductivity in these compounds. CeO(F)FeAs ($T_C^{\text{bulk}} = 41 \pm 1 \text{ K}$) pioneer studies showed the two superconducting gaps $\Delta_L = 9 \pm 1 \text{ meV}$, $\Delta_S = 1.6 \pm 0.2 \text{ meV}$ with $2\Delta_L/k_B T_C^{\text{bulk}} \approx 5.1$, $2\Delta_S/k_B T_C^{\text{bulk}} \approx 0.9$. In LaO(F)FeAs the two superconducting gaps values $\Delta_L = 4.5 \div 6.5 \text{ meV}$, $\Delta_S = 0.8 \div 1.3 \text{ meV}$ were determined, leading to the BCS-ratios $2\Delta_L/k_B T_C^{\text{local}} = 4.2 \div 5.6$ and $2\Delta_S/k_B T_C^{\text{local}} = 0.6 \div 1.2$, respectively ($T_C^{\text{local}} = 25 \div 29 \text{ K}$). The splitting of the SGS dips observed for high-quality characteristics suggests an anisotropy of the Δ_L order parameter. IMARE spectroscopy data on FeSe break junctions point to $\Delta_L = 2.8 \pm 0.4 \text{ meV}$, $\Delta_S = 0.8 \pm 0.2 \text{ meV}$ with $2\Delta_L/k_B T_C^{\text{local}} \approx 5.7$, $2\Delta_S/k_B T_C^{\text{local}} \approx 1.5$ ($T_C^{\text{local}} = 9.7 \pm 0.5 \text{ K}$). The temperature dependences $\Delta_{L,S}(T)$ indicate the k -space proximity effect between two superconducting condensates. The large gap BCS-ratio for all the materials studied exceeds 3.52, indicating a strong electron-boson coupling in the “driving” Δ_L condensate; the small gap one appears to be less than 3.52 thus suggesting an induced superconductivity at finite temperatures in the “driven” Δ_S condensate due to a nonzero interband coupling. A linear re-

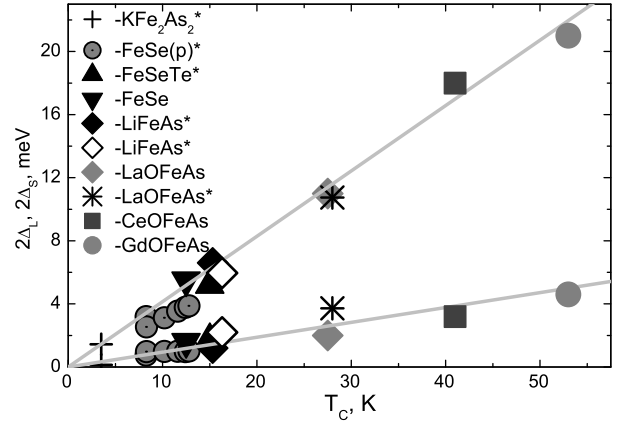


Fig. 8 Scaling of superconducting gaps with T_C for iron-based superconductors: $2\Delta_L/k_B T_C = 4.8 \pm 1.0$ and $2\Delta_S/k_B T_C = 1.1 \pm 0.4$. Star points data obtained by other groups (see Refs. in [8])

lation between superconducting gap Δ_L and magnetic resonance energy $E_{\text{res}} \approx 2\Delta_L$ is found to be valid for Fe-based superconductors.

Acknowledgements The work was supported by contract 11.519.11.60.12 of Russian MES, RFBR Grants 12-02-31269-molA, 13-02-01451-a, DFG Grants 436RUS113 and FOR 538/BU887/4, and DFG priority program (SPP1458). We thank T. Hänke, C. Hess, G. Behr, R. Klingeler and B. Büchner for the samples synthesis and the support.

References

1. A.F. Andreev, Sov. Phys. JETP 19, 1228 (1964).
2. R. Kümmel et al., Phys. Rev. B 42, 3992 (1990).
3. A. Poenicke et al., Phys. Rev. B 65, 220510 (2002).
4. G.E. Blonder et al., Phys. Rev. B 25, 4515 (1982).
5. P. Seidel, Supercond. Sci. Technol. 24, 043001 (2011).
6. Ya.G. Ponomarev, et al., Phys. Rev. B 79, 224517 (2009).
7. T.E. Shanygina et al., JETP Lett. 93, 94 (2011).
8. Ya.G. Ponomarev et al., J. Exp. Theor. Phys. 113, 459 (2011).
9. Y. Kamihara et al., J. Am. Chem. Soc. 130, 3296 (2008).
10. J. Moreland, J. W. Ekin, J. Appl. Phys. 58, 3888 (1985).
11. Yu.V. Sharvin, Zh. Eksp. Teor. Fiz. 48, 984 (1965).
12. H. Nakamura et al., J. Phys. Soc. Jpn. 78, 123712 (2009).
13. Ya.G. Ponomarev, A. V. Rakhmanina, Prib. Tehn. Eksp. 5, 120 (1970).
14. E.P. Khlybov et al., JETP Lett. 90 (2009).
15. M. Yashima, et al., J. Phys. Soc. Jpn. 78, 103702 (2009).
16. Ya.G. Ponomarev et al., Solid St. Comm. 129, 85 (2004).
17. R. Khasanov et al., Phys. Rev. Lett. 104, 087004 (2010).
18. Ya.G. Ponomarev et al., JETP Lett. 79, 484 (2004).
19. S.A. Kuzmichev et al., Solid St. Comm. 152, 119 (2012).
20. E.J. Nicol, J.P. Carbotte, Phys. Rev. B 71, 054501 (2005).
21. A.A. Golubov et al., Phys. Rev. B 51, 1073 (1995).
22. I.K. Yanson et al., Phys. Rev. B 67, 024517 (2003).
23. S. Onari et al., Phys. Rev. B, 81, 060504 (2010).
24. Shin-ichi Shamoto et al., Phys. Rev. B 82, 172508 (2010).